

PRODUCT DATASHEET



TENCATE ADVANCED COMPOSITES

TenCate Cetex® TC1100 PPS resin system

PRODUCT TYPE

Polyphenylene Sulfide (PPS)
thermoplastic resin system

SERVICE TEMPERATURE

100°C (212°F) continuous


TYPICAL APPLICATIONS

- Primary aircraft structures
- Secondary aircraft structures
- Engine nacelles

KEY PROPERTIES



Low FST values



Chemical resistant

SHELF LIFE

Indefinite at 25°C (77°F)

PRODUCT DESCRIPTION

TenCate Cetex® TC1100 is a semi-crystalline polyphenylene sulfide (PPS) thermoplastic composite offering outstanding toughness and excellent chemical and solvent resistance. The material is inherently flame resistant with low smoke emission. It exceeds 35/35 OSU and is qualified at Airbus and Boeing for multiple structural applications.

TenCate Cetex® TC1100 is typically supplied in 3.66m x 1.22m (12 ft x 4 ft) pre-consolidated reinforced laminate (RTL) utilising either woven carbon or E-glass to the customer's designated ply count and orientation. High strength and intermediate modulus carbon UD tape versions are offered in a standard 152 mm (6 inch) width or alternative 305 mm widths (12 inch). Alternative narrower slit widths for ATL processing may be available through secondary slitting.

In addition, lightning strike material can be incorporated on laminates and the laminates can be textured. By utilizing preconsolidated sheets and avoiding hand lamination, the customer can significantly reduce the cycle time required to produce a finished part. In addition, thermoplastics have the unique capability of allowing parts to be welded, folded, etc., to facilitate lower part count structures.

TYPICAL PROPERTIES OF NEAT RESIN

| | |
|---|---|
| Specific gravity | 1.35 g/cc |
| T _g | 90°C (194°F) |
| Melt temperature (T _m)..... | 280°C (536°F) |
| Dielectric constant..... | 3.20 at 1 MHz |
| Loss tangent..... | 0.0013 at 1 MHz |
| Moisture absorption | 0.02% |
| Flammability..... | V-0 |
| Tensile strength..... | 90.3 MPa (13.1 ksi) |
| Tensile modulus | 3,800 MPa (0.551 Msi) |
| Elongation at yield | 3% |
| Poisson's ratio | 0.36 |
| Compression strength..... | 148 MPa (21.5 ksi) |
| Compression modulus..... | 2,965 MPa (0.43 Msi) |
| Flexural strength | 125 MPa (18.1 ksi) |
| Flexural modulus..... | 3,725 MPa (0.54 Msi) |
| Izod unnotched | 199 kJ/m ² (94.6 ft-lb/in ²) |
| Izod notched..... | 15.6 kJ/m ² (7.4 ft-lb/in ²) |
| CTE | 52.2 ppm/°C (29 ppm/°F) |
| Thermal conductivity..... | 0.19 W/m-°K |
| Outgassing TML..... | 0.04% |
| Outgassing CVCM..... | 0.00% |
| WVR | 0.00% |
| Fluid resistance..... | Excellent |

PRODUCT DATASHEET



TENCATE ADVANCED COMPOSITES

TenCate Cetex® TC1100 PPS resin system

MECHANICAL PROPERTIES - TENCATE CETEX® TC1100 HIGH STRENGTH UD TAPE

Carbon AS4A 12K UD, 221 gsm FAW, 34% RC (59% fibre by volume)

| Property | Condition | Test Method | Result | |
|--|-----------|-------------|----------|----------|
| Tensile strength (0°) | RTD | ASTM D 3039 | 294 ksi | 2020 MPa |
| Tensile modulus (0°) | RTD | ASTM D 3039 | 19.5 Msi | 134 GPa |
| Poisson's ratio | RTD | ASTM D 3039 | 0.33 | |
| Tensile strength (90°) | RTD | ASTM D 3039 | 5.7 ksi | 39 MPa |
| Tensile modulus (90°) | RTD | ASTM D 3039 | 1.4 Msi | 10 GPa |
| Compressive strength (0°) | RTD | ASTM D 6641 | 160 ksi | 1100 MPa |
| Compressive modulus (0°) | RTD | ASTM D 6641 | 17 Msi | 117 GPa |
| In Plane Shear Strength (±45° tension) | RTD | ASTM D 3518 | 11.9 ksi | 82 MPa |
| In Plane Shear Modulus (±45° tension) | RTD | ASTM D 3518 | .50 Msi | 3.5 GPa |
| Flexural strength (90°) | RTD | ASTM D 790 | 9.9 ksi | 68 MPa |
| Open hole compressive strength | RTD | ASTM D 6484 | 38.7 ksi | 267 MPa |
| Compression after impact after 270 in-lb impact (30.5 J) | RTD | ASTM D 7137 | 31.4 ksi | 216 MPa |

⁽¹⁾ Consolidated ply thickness average is 0.21 mm (.0082")

⁽²⁾ Density is 1.6 g/cm³ (0.058 lb/in³)

MECHANICAL PROPERTIES - TENCATE CETEX® TC1100 INTERMEDIATE MODULUS UD TAPE

Carbon IM7 12K UD, 146 gsm FAW, 34% RC, (59% fibre by volume)

| Property | Condition | Test Method | Result | |
|---------------------------|-----------|-------------|----------|----------|
| Tensile strength (0°) | RTD | ASTM D 3039 | 400 ksi | 2760 MPa |
| Tensile modulus (0°) | RTD | ASTM D 3039 | 22.1 Msi | 152 GPa |
| Tensile strength (90°) | RTD | ASTM D 3039 | 5.7 ksi | 39 MPa |
| Tensile modulus (90°) | RTD | ASTM D 3039 | 1.4 Msi | 10 GPa |
| Compressive strength (0°) | RTD | ASTM D 6641 | 186 ksi | 1280 MPa |
| Compressive modulus (0°) | RTD | ASTM D 6641 | 18 Msi | 124 GPa |
| Flexural strength (90°) | RTD | ASTM D 790 | 9.5 ksi | 65 MPa |

Prepreg aeral weight 218gsm

PRODUCT DATASHEET



TENCATE ADVANCED COMPOSITES

TenCate Cetex® TC1100 PPS resin system

LAMINATE DATA USED E-GLASS 7781, 296GSM FAW, 37% RC (47.5% BY VOLUME)

Specific gravity 1.92 g/cc, T_g 90°C, T_m 280°C

| Property | Condition/Result | | Condition/Result | | Condition/Result | | Condition/Result | | Condition/Result | |
|--------------------------------|------------------|-------------------------|------------------|-------------------------|------------------|-------------------------|------------------|-------------------------|--------------------|--------------------------|
| Tensile strength 0° | CTD | 65.6 ksi (452 MPa) | RTD | 49.3 ksi (339 MPa) | ETD | 40.5 ksi (279 MPa) | ETW | 41.9 ksi (289 MPa) | ETW ⁽²⁾ | 35.7 ksi (246 MPa) |
| Tensile strength 90° | CTD | 64.8 ksi (447 MPa) | RTD | 48.3 ksi (333 MPa) | ETD | 40.7 ksi (281 MPa) | ETW | 41.8 ksi (288 MPa) | ETW ⁽²⁾ | 39.6 ksi (273 MPa) |
| Tensile modulus 0° | CTD | 3.2 Msi (22.1 GPa) | RTD | 3.1 Msi (21.4 GPa) | ETD | 2.9 Msi (20.0 GPa) | ETW | 3 Msi (20.7 GPa) | ETW ⁽²⁾ | 2.8 Msi (19.3 GPa) |
| Tensile modulus 90° | CTD | 3 Msi (20.7 GPa) | RTD | 2.9 Msi (20.0 GPa) | ETD | 2.7 Msi (18.6 GPa) | ETW | 2.8 Msi (19.3 GPa) | ETW ⁽²⁾ | 2.6 Msi (17.9 GPa) |
| Compressive strength 0° | CTD | 82.1 ksi (566 MPa) | RTD | 61.6 ksi (425 MPa) | ETD | 43 ksi (297 MPa) | ETW | 33.4 ksi (230 MPa) | ETW ⁽²⁾ | 24.4 ksi (168 MPa) |
| Compressive strength 90° | CTD | 55.7 ksi (384 MPa) | RTD | 42.8 ksi (295 MPa) | ETD | 29.4 ksi (203 MPa) | ETW | 22.6 ksi (156 MPa) | ETW ⁽²⁾ | 16.9 ksi (117 MPa) |
| Compressive modulus 0° | CTD | 3.8 Msi (26.2 GPa) | RTD | 3.7 Msi (25.5 GPa) | ETD | 3.2 Msi (22.1 GPa) | ETW | 3.1 Msi (21.4 GPa) | ETW ⁽²⁾ | 2.9 Msi (20.0 GPa) |
| Compressive modulus 90° | CTD | 3.6 Msi (24.8 GPa) | RTD | 3.5 Msi (24.1 GPa) | ETD | 2.9 Msi (20.0 GPa) | ETW | 2.9 Msi (20.0 GPa) | ETW ⁽²⁾ | 2.5 Msi (17.2 GPa) |
| In-Plane Shear Strength | CTD | 15.8 ksi (109 MPa) | RTD | 11.6 ksi (80.0 MPa) | ETD | 8.6 ksi (59.3 MPa) | ETW | 9.8 ksi (67.6 MPa) | ETW ⁽²⁾ | 9.1 ksi (62.7 MPa) |
| In-Plane Shear Modulus | CTD | 0.712 Msi (4.91 GPa) | RTD | 0.539 Msi (3.71 GPa) | ETD | 0.247 Msi (1.71 GPa) | ETW | 0.208 Msi (1.44 GPa) | ETW ⁽²⁾ | 0.109 Msi (0.752 GPa) |
| Flexural strength 0° | | | RTD | 74.2 ksi (512 MPa) | | | | | | |
| Flexural strength 90° | | | RTD | 56.6 ksi (390 MPa) | | | | | | |
| Flexural modulus 0° | | | RTD | 3.3 Msi (22.8 GPa) | | | | | | |
| Flexural modulus 90° | | | RTD | 2.9 Msi (20.0 GPa) | | | | | | |
| Open hole tensile strength | | | RTD | 23 ksi (159 MPa) | | | ETW | 19.6 ksi (135 MPa) | | |
| Open hole compressive strength | | | RTD | 26.5 ksi (183 MPa) | | | ETW | 16 ksi (110 MPa) | | |
| Bearing strength yield | | | RTD | 46.1 ksi (318 MPa) | | | ETW | 26.7 ksi (184 MPa) | | |
| Bearing strength ultimate | | | RTD | 74.8 ksi (516 MPa) | | | ETW | 55.6 ksi (383 MPa) | | |
| Compression after impact | | | RTD | 24.8 ksi (171 MPa) | | | | | | |

CTD = 55°C / 67°F

ETD = 23°C / 73°F at 50% RH ETD = 80°C / 176°F

ETW = 80°C / 176°F conditioned at 70°C / 158°F at 85% RH

ETW⁽²⁾ = 100°C / 212°F conditioned at 70°C / 158°F at 85% RH

Average results according to Mil-R-17; test methods vary

FLAMMABILITY PROPERTIES

| | OSU | | Flammability | | | SMOKE (4 min) | | TOXICITY | | | | | | |
|------------------------|--------------|--------------|--------------|-------------|------------|---------------|---------|----------|----|-----|-----|----|-----|-----|
| | Heat Release | Release Rate | Burn Length | After Flame | Drip Flame | Non-flaming | Flaming | HCN | CO | NOx | SO2 | HF | HCl | HBr |
| 5 plies of 7781 / PEI | 14 | 21 | 1.9 mm | 0sec | N/D | | | | | | | | | |
| 4 plies of 3k PW / PPS | | | | | | | | 9.03 | 9 | | 1 | 17 | 1 | 1 |

Flammability & Heat Release - FAR 25.853.
Smoke Density & Toxicity - ATS 1000.001

PRODUCT DATASHEET



TENCATE ADVANCED COMPOSITES

TenCate Cetex® TC1100 PPS Resin System

LAMINATE DATA USED CARBON T300 3K, 5HS, 280GSM FAW, 43% RC (50% BY VOLUME)

Specific gravity 1.55 g/cc, T_g 90°C, T_m 280°C

| Property | Condition/Result | | Condition/Result | | Condition/Result | | Condition/Result | | Condition/Result | |
|--------------------------------|------------------|-------------------------|------------------|-------------------------|------------------|-------------------------|------------------|-------------------------|--------------------|-----------------------|
| Tensile strength 0° | CTD | 115 ksi (790 MPa) | RTD | 110 ksi (757 MPa) | ETD | 106 ksi (730 MPa) | ETW | 110 ksi (756 MPa) | ETW ⁽²⁾ | 96 ksi (665 MPa) |
| Tensile strength 90° | CTD | 109 ksi (750 MPa) | RTD | 109 ksi (754 MPa) | ETD | 93.6 ksi (645 MPa) | ETW | 101 ksi (698 MPa) | ETW ⁽²⁾ | 94 ksi (650 MPa) |
| Tensile modulus 0° | CTD | 7.7 Msi (53.1 GPa) | RTD | 8.1 Msi (55.8 GPa) | ETD | 8.2 Msi (56.5 GPa) | ETW | 8.2 Msi (56.5 GPa) | ETW ⁽²⁾ | 7.8 Msi (53.7 GPa) |
| Tensile modulus 90° | CTD | 7.6 Msi (52.4 GPa) | RTD | 7.8 Msi (53.8 GPa) | ETD | 7.6 Msi (52.4 GPa) | ETW | 7.6 Msi (52.4 GPa) | ETW ⁽²⁾ | 6.5 Msi (45.2 GPa) |
| Compressive strength 0° | CTD | 98 ksi (676 MPa) | RTD | 93.3 ksi (643 MPa) | ETD | 80.9 ksi (558 MPa) | ETW | 83.8 ksi (577 MPa) | | |
| Compressive strength 90° | CTD | 101 ksi (698 MPa) | RTD | 92.4 ksi (637 MPa) | ETD | 76.3 ksi (526 MPa) | ETW | 77.5 ksi (534 MPa) | | |
| Compressive modulus 0° | CTD | 7.2 Msi (49.6 GPa) | RTD | 7.5 Msi (51.7 GPa) | ETD | 7.5 ksi (51.7 GPa) | ETW | 7.5 Msi (51.7 GPa) | | |
| Compressive modulus 90° | CTD | 7.2 Msi (49.6 GPa) | RTD | 7.5 Msi (51.7 GPa) | ETD | 7.4 ksi (51.0 GPa) | ETW | 7.4 Msi (51.0 GPa) | | |
| In-Plane Shear Strength | CTD | 19 ksi (131 MPa) | RTD | 17.2 ksi (119 MPa) | ETD | 15.7 ksi (108 MPa) | ETW | 15.1 ksi (104 MPa) | | |
| In-Plane Shear Modulus | CTD | 0.642 Msi (4.43 GPa) | RTD | 0.586 Msi (4.04 GPa) | ETD | 0.384 Msi (2.65 GPa) | ETW | 0.435 Msi (3.00 GPa) | | |
| Flexural strength 0° | CTD | 151 ksi (1043 MPa) | RTD | 149 ksi (1027 MPa) | ETD | 138 ksi (954 MPa) | ETW | 142 ksi (977 MPa) | | |
| Flexural strength 90° | CTD | 121 ksi (834 MPa) | RTD | 121 ksi (831 MPa) | ETD | 115 ksi (794 MPa) | ETW | 107 ksi (739 MPa) | | |
| Flexural modulus 0° | CTD | 8.6 Msi (59.3 GPa) | RTD | 8.7 Msi (60.0 GPa) | ETD | 8.4 Msi (57.9 GPa) | ETW | 8.7 Msi (60.0 GPa) | | |
| Flexural modulus 90° | CTD | 6.3 Msi (43.4 GPa) | RTD | 6.5 Msi (44.8 GPa) | ETD | 6.5 Msi (44.8 GPa) | ETW | 6.4 Msi (44.1 GPa) | | |
| Open hole tensile strength | CTD | 41.4 ksi (285 MPa) | RTD | 40.4 ksi (279 MPa) | | | ETW | 39.1 ksi (270 MPa) | | |
| Open hole compressive strength | CTD | 39.5 ksi (272 MPa) | RTD | 37.1 ksi (256 MPa) | | | ETW | 33.7 ksi (232 MPa) | | |
| Bearing strength yield | CTD | 71.2 ksi (491 MPa) | RTD | 65.8 ksi (454 MPa) | | | ETW | 59.9 ksi (413 MPa) | | |
| Bearing strength ultimate | CTD | 122 ksi (838 MPa) | RTD | 122 ksi (844 MPa) | | | ETW | 122 ksi (838 MPa) | | |
| Compression after impact | CTD | 32.3 ksi (223 MPa) | RTD | 31.2 ksi (215 MPa) | | | ETW | 31.6 ksi (218 MPa) | | |

CTD = 55°C / 67°F

ETD = 23°C / 73°F at 50% RH

ETD = 80°C / 176°F

ETW = 80°C / 176°F conditioned at 70°C / 158°F at 85% RH

ETW⁽²⁾ = 100°C / 212°F conditioned at 70°C / 158°F at 85% RH

TenCate Cetex® TC1100 PPS resin system

Processing guidelines for TenCate Cetex® TC1100 thermoplastic composite materials

TenCate Cetex® TC1100 thermoplastic composite materials from TenCate are processed by heating the material above the PPS melting point and moulding it and cooling it under pressure to the desired shape. Because no chemical change occurs to the PPS matrix, processing is very rapid. The quick easy processing of TenCate Cetex® materials is also made possible because of the rapid crystallization rate of the PPS matrix. The key thermal processing parameters are:

Melt temperature (T_m)..... 560°F (293°C)
Typical processing temperature..... 625°F (330°C)

TenCate can also produce TenCate Cetex® towpregs & simple profiles (round rods, ovals, rectangles, etc.). TenCate also has the capability to chop the towpregs & simple profiles into discrete length long fibre thermoplastic type materials for injection or compression moulding type processes.

Automated Processes

Below are several examples of automated processes that are utilized and available in the market today. Both processes utilize similar premises in that they eliminate the need for autoclave consolidation of thermoplastic composite parts, thereby dramatically reducing the cost of producing continuous fibre composite structures.

1. Fibre placement with in situ consolidation

This process utilizes narrow width tapes typically 6 – 25 mm (0.25 – 1 inches) as its composite material medium and lays down, heats via hot gas, laser, or other heating methods and consolidates the composite material onto the tool, in situ, without the need for further consolidation processes.



Photo courtesy of Automated Dynamics
www.automateddynamics.com



Photo courtesy of AFPT
www.afpt.de

2. Rapid lamination / forming

This process uses wider UD tapes typically 50 mm (≥ 2 inches) width to rapidly lay down and consolidate the thermoplastic composite material into an engineered laminate structure that can then be transformed into parts via a secondary compression thermoforming process.

Automated tape laying of tailored blank followed by consolidation

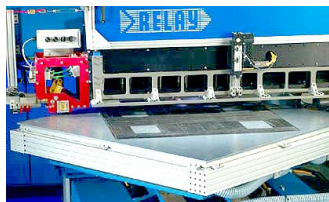


Photo courtesy of FibreForge
www.fibreforge.com

The consolidated flat laminate is then thermoformed to a 3D final shape



Photo courtesy of TenCate

TenCate Cetex[®] TC1100 PPS resin system

3. Continuous compression moulding

In this multi-step process, multiple plies of thermoplastic UD tape is heated in a mould and pressed into a laminate. This laminate is then pressed into a mould and thermoformed to the desired profile. A final step then moulds with heat and gentle pressure into the curved profile through a process called continuous compression moulding. Items such as clips, rails, beams and profile are manufactured in this type of process.



Photo courtesy of ACM / Xperion Aerospace
www.acm-fn.de

Press lamination: A laminate can be press moulded from any TenCate Cetex[®] prepreg by stacking two or more plies in the desired orientation into a picture frame mould, transferring the assembly to a heated platen press where it is brought to approximately 320°C (610°F) at contact pressure until the material reaches temperature. The pressure should then be increased to 7-21 bar (100-400 psi) and held for approximately 15-30 minutes.

Autoclave lamination: Autoclave consolidation is used for fabricating laminates from any TenCate Cetex[®] prepreg tape. Individual layers are stacked in the desired orientation and vacuum bagged (vacuum should be maintained throughout the entire process). A high temperature bagging material, such as Kapton polyimide should be used. The assembly should then be placed in the autoclave and brought to approximately 320°C (610°F), at which time the pressure is increased from ambient to 7-10 bar (100-150 psi) and maintained for around 20-30 minutes. The part should then be cooled to room temperature at a 5-20°C cool down rate to maintain crystallinity.

Thermoforming laminates into shapes: Thermoforming is used to convert a flat consolidated continuous fibre reinforced laminate into a complex shape with no change in starting laminate thickness. The laminate should be heated to around 320°C (610°F) in an infrared or similar oven and then quickly transferred to a matched core/cavity mould where it can be formed at 10-40 bar (150-600 psi). For optimum properties and formability, heating of the composite laminate should take no longer than 8 minutes. Overall part production cycle times are between 2-10 minutes, depending on material thickness and part geometry. Production tooling consists of machined aluminum halves, one that has a compliant layer of cast silicone, and an associated laminate tensioning system to prevent wrinkling within the part being thermoformed.

Cutting and machining: Thermoplastic composite laminates and thermoformed parts can be machined with feed rates and tip speeds similar to those used when machining brass. The following are some general guidelines:

| | |
|---------------------|--|
| Circular saw: | Diamond-grit-edge blade of 220 grit. Blade speed: 1830 mpm (6000 fpm) with water or soap solution as coolant. Feed rates depend on thickness. |
| Turning operations: | Cutting speed: 105-120 mpm (350-400 fpm) for high speed tools, 180-455 mpm (1500-2500 fpm) for Stellite or carbide tools, and 600-1200 mpm (2000-4000 fpm) for diamond tools |
| Milling operations: | Tip speed: 75-135 mpm (250-450 fpm) for carbide and diamond tools Plunge feed rate: 0.15-0.30 mpm (0.5-1 fpm) |

TenCate Cetex® TC1100 PPS resin system

| | |
|----------------------|---|
| Drilling operations: | Feed rate: 0.2-0.4 mm/rev (0.008-0.016 in/rev) Drill speed: 45-90 mpm (150-300 fpm) Drill point angles: 60° for thin parts, 90° for thick parts Clearance angle: 15° |
| Tapping: | Tool rake of 0° to 5° negative |
| Shearing: | Thicknesses up to 3.2 mm (0.125 inch) |

Joining: Thermoplastic composites can be joined via mechanical fasteners, adhesive bonding, or fusion welding.

Strong adhesive bonds are possible with epoxy adhesives when PPS surfaces are cleaned with a suitable degreasing solvent (i.e. MEK), abrasive treatment (i.e., abrasion wheels, sand paper, or grit blasted with #100 or #200 Aluminum Oxide). The surface energy may also be enhanced by flame/corona treatment, chromic acid etching, laser treatment, or plasma techniques. Epoxy films or pastes with cure temperatures up to 177°C (350°F), anaerobics, silicone sealers, and cyanoacrylates are effective adhesives depending on specific requirements.

TenCate Cetex® TC1100 based composites may also be bonded using conventional thermoplastic welding techniques. PPS based materials have very high melt temperatures and considerable amounts of energy must be put into the interface to achieve a good bond. Satisfactory results have also been obtained using induction or resistance welding.

Painting: TenCate Cetex® TC1100 composite surfaces can be painted with a variety of products. It is recommended that a paintable (non-silicone) mould release be used, if possible, during the moulding of all surfaces to be painted. If a silicone or Teflon mould release is used during moulding, laminate and part surfaces may require abrasion prior to painting. In all cases, surfaces must be wiped with a suitable solvent (e.g. MEK, DuPont 3919S) to remove oils, release agents, or other impurities.

Health & Safety: Health and safety information on handling and processing TenCate composite materials is described in a Safety Data Sheet. To obtain this or any other information about TenCate PPS thermoplastic composite materials, contact your local TenCate Advanced Composites office.

Revised 09/2016

All data given is based on representative samples of the materials in question. Since the method and circumstances under which these materials are processed and tested are key to their performance, and TenCate Advanced Composites has no assurance of how its customers will use the material, the corporation cannot guarantee these properties.

TenCate, [TenCate] Cetex® and all other related characters, logos and trade names are claims and/or registered trademarks of Koninklijke Ten Cate N.V. and/or its subsidiaries in one or more countries. Use of trademarks, trade names and other IP rights of TenCate without express written approval of TenCate is strictly prohibited.

Page 7 of 7 CETEX_TC1100_V4_DS_090116