

PRODUCT DATA SHEET

DESCRIPTION

Toray C640 is a cyanate ester resin system suitable for curing between 70°C (158°F) and 135°C (275°F). The medium viscosity resin is pre-impregnated into high-performance fibers such as carbon, glass and aramid. The system is capable of withstanding very high temperatures and is inherently flame-retardant. After a suitable post cure, the glass transition temperature can be increased to as high as 335°C (635°F).

FEATURES

- ▶ Flexible low to medium cure schedules 70°C (158°F) to 135°C (275°F)
- ▶ 4 days shelf life at ambient temperatures
- ▶ Inherently flame retardant with low toxic gas and smoke generation
- ▶ Excellent drapeability—complex shapes easily formed
- ▶ Maximum T_g (DMTA—onset) 335°C (635°F)
- ▶ Good dimensional stability and thermal durability up to 250°C (482°F) after post cure
- ▶ Excellent surface finish
- ▶ Low volatile content—no solvents used during processing

PRODUCT TYPE

70°C (158°F) to 135°C (275°F) Cure

Flexible Cure High Temperature Resistant Cyanate Ester Component Prepreg

TYPICAL NEAT RESIN PROPERTIES

Density	1.28 g/cm ³
T _g (DMTA) after 2 hours at 250°C (482°F) post cure	Onset: 285°C (545°F); Peak tan δ: 334°C (633°F)
T _g (DMTA) after 2 hours at 300°C (572°F) post cure	Onset: 335°C (635°F); Peak tan δ: 409.5°C (769°F)

TYPICAL APPLICATIONS

- ▶ High temperature applications such as brake ducts

SHELF LIFE

Out Life: 4 days at 20°C (68°F)

Storage Life: 6 months at -18°C (0°F)

Out life is the maximum time allowed at room temperature before cure.

To avoid moisture condensation

Following removal from cold storage, allow the prepreg to reach room temperature before opening the polythene bag. Typically, the thaw time for a full roll of material will be 4 to 6 hours.



Contact us for more information:

North America/Asia/Pacific

e explore@toraytac-usa.com

t +1 408 465 8500

Europe/Middle East/Africa

e explore@toraytac-europe.com

t +44 (0)1773 530899

PRODUCT DATA SHEET

TYPICAL LAMINATE PROPERTIES

HS0804 – Carbon 205 gsm 2x2 Twill T300 (3K) 42% RC				
Property	Condition	Method	Results	
Tensile Strength*	RTD	ISO 527-4	509 MPa	156 ksi
Tensile Modulus*	RTD	ISO 527-4	58.4 GPa	8.5 Msi
Tensile Strength*	180°C (356°F)	ISO 527-4	570 MPa	83 ksi
Tensile Modulus *	180°C (356°F)	ISO 527-4	59.2 GPa	8.6 Msi
Poisson's Ratio	RTD		0.04	
Poisson's Ratio	180°C (356°F)		0.05	
Compression Strength *	RTD	EN 2580	652 MPa	95 ksi
Compression Modulus *	RTD	EN 2580	57.3 GPa	8.3 Msi
Compression Strength *	180°C (356°F)	EN 2580	594 MPa	86 ksi
Compression Modulus *	180°C (356°F)	EN 2580	57.9 GPa	8.4 Msi
Compression Strength *	250°C (482°F)	EN 2580	594 MPa	86 ksi
In-Plane Shear Strength	RTD	ISO 14129	67 MPa	10 ksi
In-Plane Shear Modulus	RTD	ISO 14129	4.02 GPa	0.6 Msi
In-Plane Shear Strength	180°C (356°F)	ISO 14129	69 MPa	10 ksi
In-Plane Shear Modulus	180°C (356°F)	ISO 14129	3.14 GPa	0.5 Msi
In-Plane Shear Strength	250°C (482°F)	ISO 14129	61 MPa	9 ksi
Interlaminar Shear Strength	RTD	ISO 14130	32 MPa	5 ksi
Interlaminar Shear Strength	180°C (356°F)	ISO 14130	40 MPa	6 ksi
Interlaminar Shear Strength	250°C (482°F)	ISO 14130	37 MPa	5 ksi

Cured for 10 hours at 80°C (177°F) and post cured for 2 hours at 300°C (572°F)
 *Results normalized to 55% Vf

OUTLIFE TRIAL - PREPREG LEFT FOR 5 DAYS AT 20°C (68°F) PRIOR TO MOLDING

HS0804 – Carbon 205 gsm 2x2 Twill T300 (3K) 42% RC				
Property	Condition	Method	Results	
Interlaminar Shear Strength	RTD	ISO 14130	36 MPa	5 ksi
Interlaminar Shear Strength	180°C (356°F)	ISO 14130	41 MPa	6 ksi
Interlaminar Shear Strength	250°C (482°F)	ISO 14130 1	41 MPa	6 ksi


Cured for 10 hours at 80°C (177°F) and post cured for 2 hours at 300°C (572°F)
 *Results normalized to 55% Vf

PRODUCT DATA SHEET


RECOMMENDED CURE TIMES

Cure Temperature	Recommended Dwell Times
70°C (158°F)	18 hours
80°C (176°F)	10 hours
100°C (212°F)	4 hours
120°C (248°F)	2 hours
135°C (275°F)	1 hour

INITIAL MINIMUM 80°C (176°F) CURE SCHEDULE

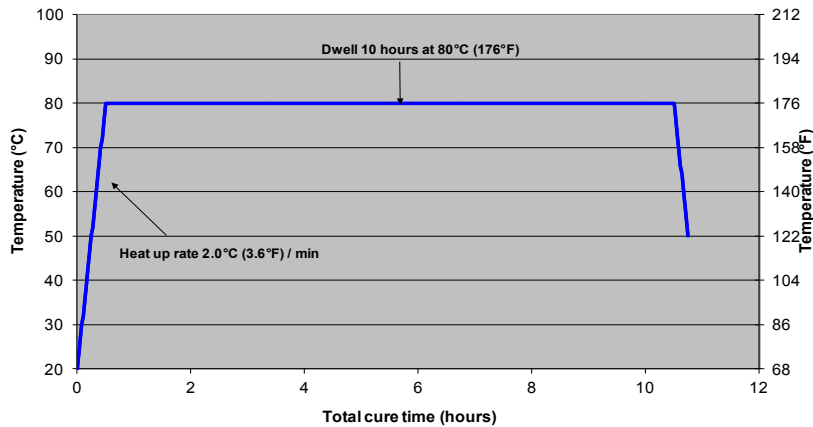

INITIAL MINIMUM 135°C (275°F) CURE SCHEDULE

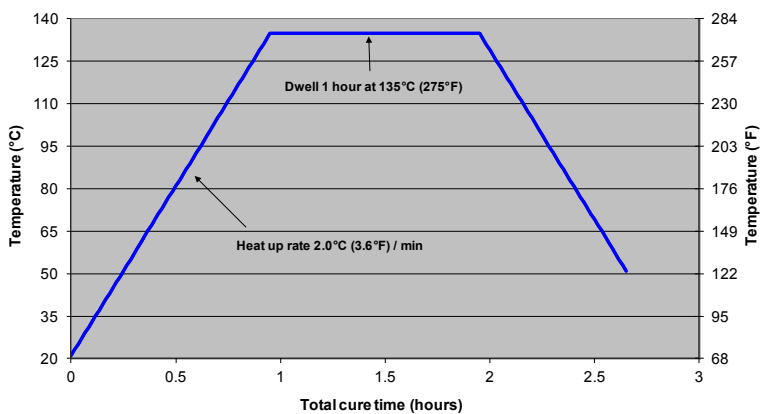

RECOMMENDED CURE CYCLE

- ▶ Increase autoclave pressure to 1.4 bar (20 psi) with vacuum applied (29 in Hg)
- ▶ Vent to atmosphere and raise pressure to 6.2bar (90psi) (or maximum allowed by core material)
- ▶ Increase air temperature at 2°C (3.6°F)/min to the required dwell temperature (see table and graph on page 2)
- ▶ Dwell for the recommended time period and cool to 50°C (122°F) prior to removal of the pressure
- ▶ To obtain the maximum T_g it is essential that a suitable postcure is carried out. e.g., ramp from the cure dwell temperature to 300°C (572°F) at 20°C (36°F)/hour and hold for 2 hours minimum. Cool to 60°C (140°F) at 3°C (5.4°F) per minute. This will produce a laminate with T_g 335°C (635°F) (DMTA Onset)

PRODUCT DATA SHEET

EXOTHERM

In certain circumstances, such as the production of thick section laminates rapid heat-up rates or highly insulating masters, C640 can undergo exothermic heating leading to rapid temperature rise and component degradation in extreme cases.

Where this is likely, a cure incorporating an intermediate dwell is recommended in order to minimize the risk.

MOISTURE EFFECTS

Under certain conditions moisture will react with Cyanate Ester functional groups to produce carbon dioxide gas, and at elevated temperatures trapped gas will expand and may cause the laminate to blister.

Care must be taken when defrosting the prepreg to minimize any condensation. All tooling and any molded inserts should be dried prior to use to ensure any absorbed moisture is removed. It is recommended that the post cure takes place immediately after the cure is completed.

HANDLING SAFETY

Observe established precautions for handling epoxy resins and fibrous materials—wear gloves. For further information, refer to Safety Data Sheet.

PROCESSING

Following removal from refrigerated storage, allow the prepreg to reach room temperature before opening the polythene bag to avoid moisture condensation. Typically, the thaw time for a full roll of material will be 4 to 6 hours.

Cut patterns to size and lay-up the laminate in line with design instructions taking care not to distort the prepreg. If necessary, the tack of the prepreg may be increased by gentle warming with hot air. The lay-up should be vacuum debulked at regular intervals using a P3 (pin pricked) release film on the prepreg surface; vacuum of 980 mbar (29 in Hg) is applied for 20 minutes.

For autoclave cures, use of a nonperforated release film on the prepreg surface trimmed to within 25–30 mm of the prepreg edge is recommended for the cure cycle and a vacuum bag should be installed using standard techniques.