

PRODUCT DATA SHEET

DESCRIPTION

Toray AmberTool® HX56 is a low temperature curing epoxy composite tooling prepreg. After a suitable post cure, an end use temperature of 180°C (356°F) is achieved. Toray AmberTool® HX56 achieves an excellent surface finish for small to medium sized autoclave tooling.

FEATURES

- ▶ Excellent surface finish from autoclave curing
- ▶ Low initial cure temperature
- ▶ Maximum 180°C (356°F) tool end use temperature
- ▶ Excellent drape for complex shapes
- ▶ Available in carbon reinforcements from 205gsm to 990gsm
- ▶ 60 hours out life at 18°C (64°F)*
- ▶ Capable of freestanding post cure
- ▶ Low prepreg volatile content
- ▶ Low coefficient of thermal expansion (CTE)
- ▶ Surface machinable following post cure

PRODUCT TYPE

40–55°C (104–131°F) Curing Epoxy Tooling Prepreg with Improved Handling Properties

TYPICAL APPLICATIONS

- ▶ Small-to-medium-sized autoclave tooling with fast cure and excellent surface finish

SHELF LIFE

| | |
|----------------------|--------------------------|
| Out Life: | 60 hours at 18°C (64°F)* |
| Storage Life: | 6 months at -18°C (0°F) |

*Out life represents the product in roll format. If supplied in pre-cut squares, then out life is reduced by 12 hours.

Out life is the maximum time allowed at ambient temperature before cure.

To avoid moisture condensation:

Following removal from cold storage, allow the prepreg to reach room temperature before opening the polythene bag. Typically, the thaw time for a full roll of material will be 4 to 6 hours.

TYPICAL NEAT RESIN PROPERTIES

| | |
|---|--|
| Density | 1.23 g/cm ³ (77lbs/ft ³) at 23°C (73°F) |
| T _g (DMTA) after 190°C (374°F) post cure | Onset: 185°C (365°F); Peak tan δ: 209°C (408°F) |
| Typical CTE for a carbon tool | 3.2 x 10 ⁻⁶ /°C** |

**CTE is dependent on construction and processing. Figures quoted are based on standard 1-8-1 quasi-isotropic tooling laminates.



Contact us for more information:

North America/Asia/Pacific

e explore@toraytac-usa.com

t +1 408 465 8500

Europe/Middle East/Africa

e explore@toraytac-europe.com

t +44 (0)1773 530899

AmberTool®

TORAY_AMBERTOOL_HX56_PDS_v4.0_2021-01-25

Page 1/5


PRODUCT DATA SHEET

REINFORCEMENTS AVAILABLE

| Fibre Type | Weight (gsm) | Weave Style | Standard Resin Content w/o | Theoretical Molded Thickness (mm) |
|-----------------------------|--------------|-------------|----------------------------|-----------------------------------|
| Standard modulus 3K carbon | 205 | 2x2 twill | 46 (surface ply) | 0.26 |
| Standard modulus 12K carbon | 650 | 2x2 twill | 35 (bulk ply) | 0.65 |
| Standard modulus 24K carbon | 990 | 2x2 twill | 35 (heavy bulk ply) | 0.98 |

Other fabrics and resin weights available on request

RHEOLOGY

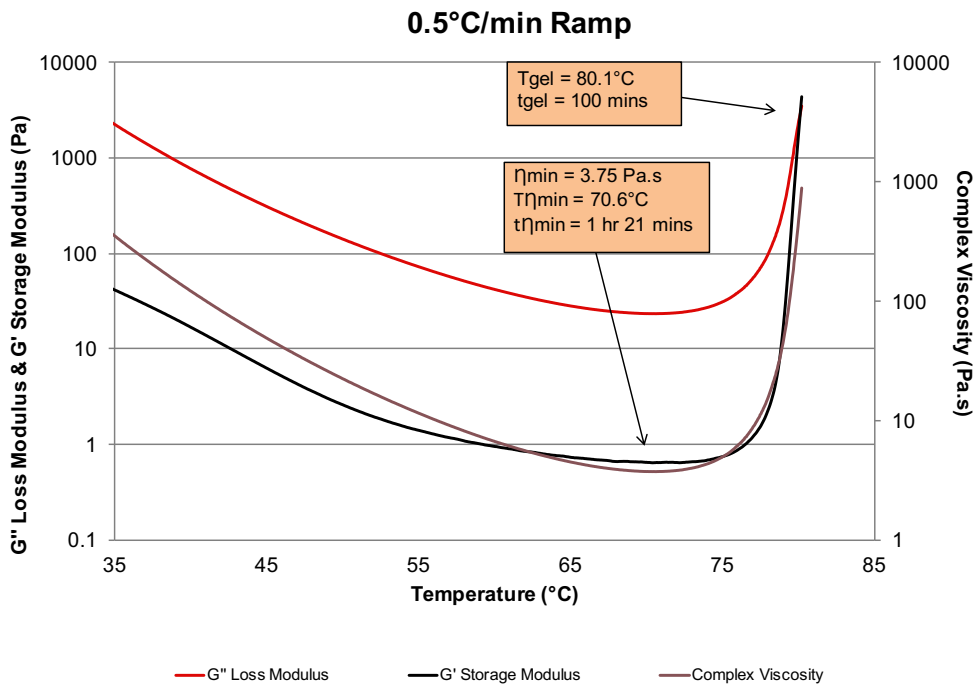


INITIAL MINIMUM CURE TIMES

| Temperature | Time (hrs) |
|--------------|------------|
| 40°C (104°F) | 18 |
| 45°C (113°F) | 12.5 |
| 50°C (122°F) | 8.5 |
| 55°C (131°F) | 6 |

PRODUCT DATA SHEET

INITIAL MINIMUM CURE SCHEDULE

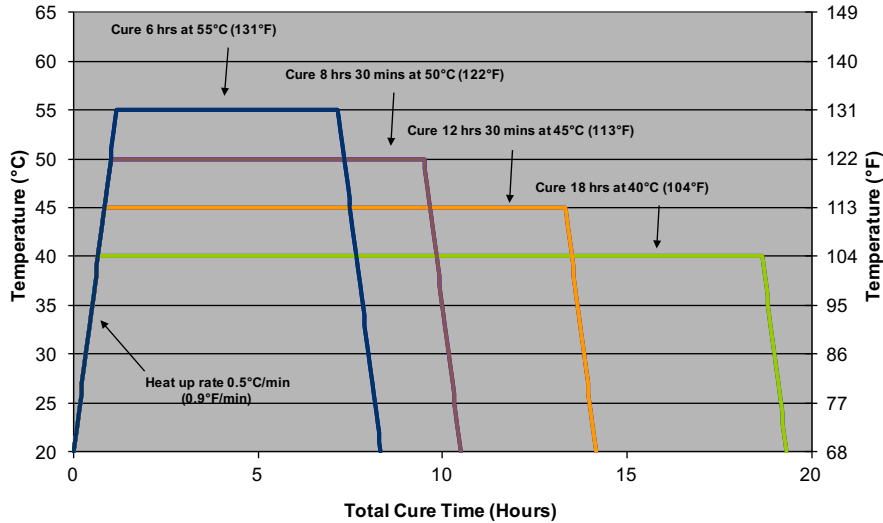

Alternative cure cycles at higher temperature may be used e.g., 4 hours at 60°C (140°F)
 Caution: Toray AmberTool® HX56 prepreg contains a reactive resin system and care must be taken to avoid exothermic heating during the initial cure. Avoid exceeding 65°C (149°F) during the initial cure.


POST CURE TIME

| Post Cure Schedule A | | |
|---|----------------------------------|-------------------|
| Ramp | 1°C (1.8°F)/min to 60°C (140°F) | Dwell for 2 hours |
| Ramp | 1°C (1.8°F)/min to 90°C (194°F) | Dwell for 1 hour |
| Ramp | 1°C (1.8°F)/min to 120°C (248°F) | Dwell for 1 hour |
| Ramp | 1°C (1.8°F)/min to 150°C (302°F) | Dwell for 1 hour |
| Ramp | 1°C (1.8°F)/min to 170°C (338°F) | Dwell for 1 hour |
| Ramp | 1°C (1.8°F)/min to 190°C (374°F) | Dwell for 6 hours |
| Cool to 50°C (122°F) at 2.5°C/min (4.5°F/min) | | |

Following the initial cure, it is essential to carry out a post cure in order to develop the glass transition temperature to a level suitable for the end use temperature of the tool. Laminates may be post cured unsupported, provided that the slow ramp-rates recommended in schedule A are observed. This allows time for the T_g to step ahead of the oven temperature throughout the post cure, thus preventing the matrix from softening significantly.


PRODUCT DATA SHEET

POST CURE SCHEDULE A

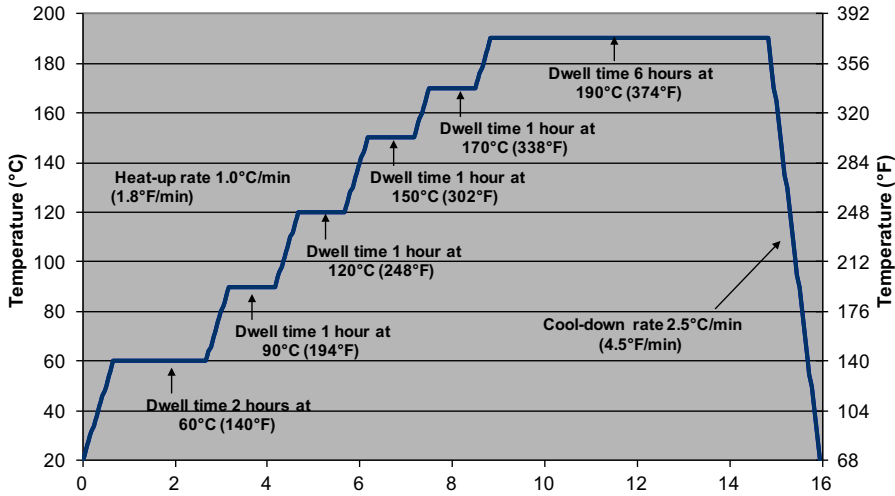

POST CURE SCHEDULE B

An alternative post cure schedule may also be used as follows.

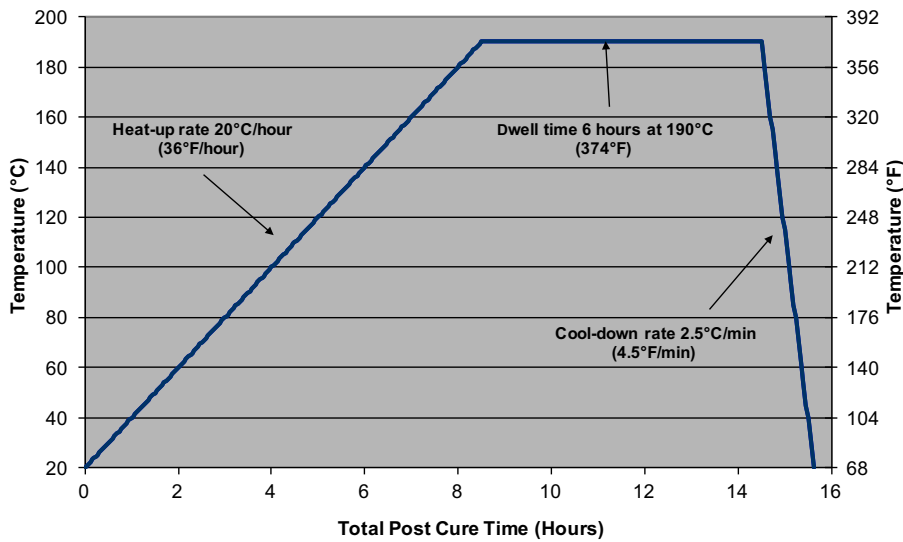

PRODUCT DATA SHEET

HANDLING SAFETY

Observe established precautions for handling epoxy resins and fibrous materials. Ensure adequate ventilation and wear gloves and protective clothing. For further information, refer to our Safety Data Sheet available from Toray Advanced Composites.

PROCESSING

Processing parameters and instructions are provided in the Toray AmberTool® material processing information guide from Toray Advanced Composites at www.toraytac.com/tooling.

TORAY_AMBERTOOL_HX56_PDS_v4.0_2021-01-25 Page 5/5

© 2019–2021 Toray Advanced Composites. All data given is based on representative samples of the materials in question. Since the method and circumstances under which these materials are processed and tested are key to their performance, and Toray Advanced Composites has no assurance of how its customers will use the material, the corporation cannot guarantee these properties. Toray®, (Toray) AmberTool®, (Toray) Cetex®, (Toray) MicroPly™, and all other related characters, logos, and trade names are claims and/or registered trademarks of Toray Industries Inc. and/or its subsidiary companies in one or more countries. Use of trademarks, trade names, and other IP rights of Toray Industries Inc. without prior written approval by such is strictly prohibited.